

# NXT Z\* 45 Silane

Coupling Agent for Silica-Reinforced  
 Tire Tread Compounds



## MARKETING BULLETIN

## SILANES - TIRE & RUBBER

NXT Z 45 silane offers a virtually ethanol emission-free option for enhanced tire performance with overall systems cost-efficiencies for tire manufacturers.


NXT Z 45 silane is an oligomeric combination of mercapto and thiocarboxylate functional silanes. It can help improve dynamic and physical properties, reduce overall manufacturing costs through improved processing, lower use levels and virtually eliminate ethanol emissions.

Silica compounds coupled with NXT Z 45 silane generally exhibit improved silica dispersion, easier mixing and faster pliable processing. The free mercaptan functionality helps provide high reactivity and increased coupling. The blocked mercaptan aids silica dispersion to improve processability. Scorch safety can be increased by the partial or complete substitution of diphenylguanidine (DPG) with tetrabenzylthiuram disulfide (TBzTD) in the cure package. Compounds containing NXT Z 45 silane can exhibit lower Payne Effect, improved tan  $\delta$  values and better resilience properties.

### Key Features and Typical Benefits

- Fewer non-productive mixing steps
- Reduced compound viscosity
- Faster extrusion
- Improved Payne Effect
- Increased resilience
- Decreased tan  $\delta$  max
- Excellent dynamic properties at low temperature (-20 °C to +10 °C)
- Reduced heat build-up (HBU)
- Lower use level than standard silanes

### Chemical Structure

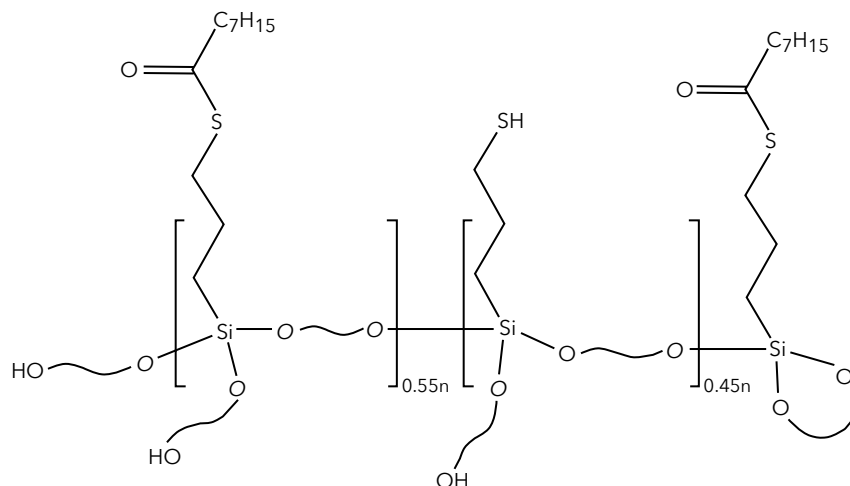

**Mercapto - Thiocarboxylate Oligomer (Mol. Wt. 440)**

Table 1: Typical Silica-Reinforced Tire Tread Formulation Used to Evaluate NXT Z 45 Silane

Ingredients	Compounds with DPG (2.0 phr)			Compounds with TBzTD (0.3 phr)		
	S2	S4	NXT Z 45 Silane	S2	S4	NXT Z 45 Silane
<b>NP1</b>						
Buna VSL 5025-1, OE	96.3	96.3	96.3	96.3	96.3	96.3
Buna CB 24	15.0	15.0	15.0	15.0	15.0	15.0
TSR-20	15.0	15.0	15.0	15.0	15.0	15.0
Zeosil 1165MP	80.0	80.0	80.0	80.0	80.0	80.0
N-330 CB	10.0	10.0	10.0	10.0	10.0	10.0
Sundex 8125 Proc. Oil	5.0	5.0	5.0	5.0	5.0	5.0
6PPD	2.0	2.0	2.0	2.0	2.0	2.0
MC Wax	1.5	1.5	1.5	1.5	1.5	1.5
<b>TESPD, S2 silane<sup>(1)</sup></b>	<b>5.64</b>			<b>5.64</b>		
<b>TESPT, S4 silane<sup>(2)</sup></b>		<b>6.40</b>			<b>6.40</b>	
<b>NXT Z 45 silane</b>			<b>5.30</b>			<b>5.30</b>
ZnO	2.5	2.5	2.5	2.5	2.5	2.5
Steric Acid	2.0	2.0	2.0	2.0	2.0	2.0

(1) S2 (TESPD) silane and S4 (TESPT) silane containing compounds were formulated having equivalent number of silane molecules (2 molecules per mole) and total sulfur content.

(2) The NXT Z 45 silane compounds contained slightly less silane molecules and total sulfur content than the S2 and S4 compounds.

Table 2: Typical Cure Package for Silica-Reinforced Tire Tread Formulation Using Standard Sulfur Silane as a Coupling Agent

Ingredients	phr	Description
<b>NP2</b>		
Remill	–	–
<b>FM</b>		
Sulfur	variable	Varies per silane
CBS	2.0	N-cyclohexyl-2-benzothiazolesulfenamide
DPG	2.0	N,N-Diphenylguanidine

Product formulations are included as illustrative examples only. Momentive makes no representation or warranty of any kind with respect to any such formulations, including, without limitation, concerning the efficacy or safety of any product manufactured using such formulations.


General Processing Considerations

Please refer to Table 5 for details regarding mixing procedures using NXT Z 45 silane.

Dynamic properties with NXT Z 45 silane compounds are typically superior to standard S2 (TESPD) and S4 (TESPT) silane compounds in the 60-110 phr equivalent silica loading range. The unique design of the NXT Z 45 silane is essentially ethanol free.


Significant improvements in compound properties may be achieved by mixing NXT Z 45 with the standard cure package seen in Table 2. However, if more scorch safety is needed (see Figure 1), then adding approximately 0.3 phr of TBzTD and completely eliminating DPG can increase scorch safety by almost 300% without loss of compound properties (see Figures 1-6, and Table 3). If some DPG is desired, then using a cure package of CBS 2.0 phr, DPG 0.5 phr and TBzTD 0.2 phr can achieve similar scorch safety and compound properties (data not shown).

Figure 1: Cure Curve Comparison of S2 (TESPD) Silane, S4 (TESPT) Silane, and NXT Z 45 Silane in Rubber Compounds

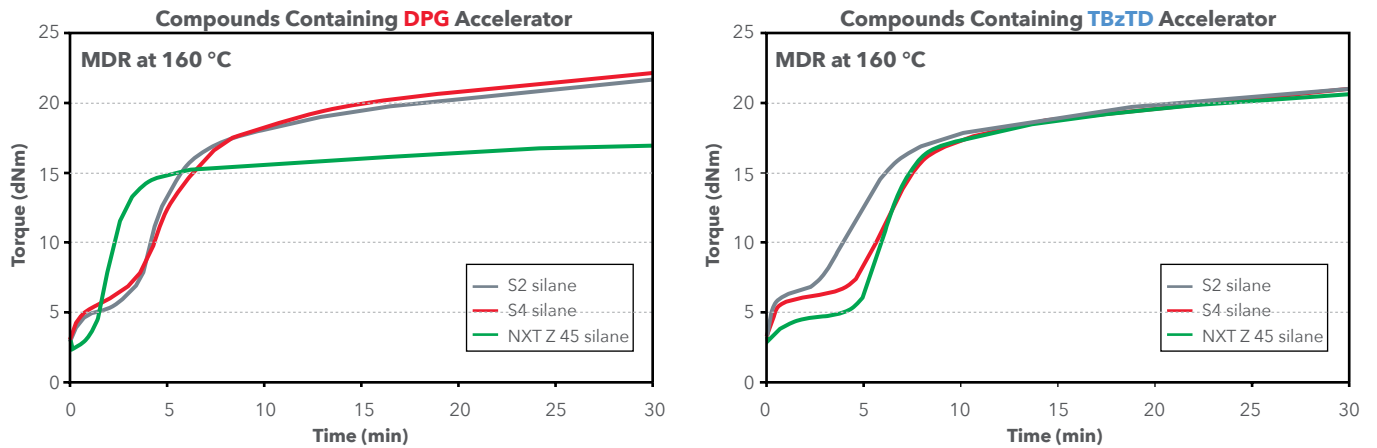

Note: Test results. Actual results may vary.

Figure 2: Comparison of Batch Viscosities of S2 (TESPD) Silane, S4 (TESPT) Silane or NXT Z 45 Silane in Rubber Compounds

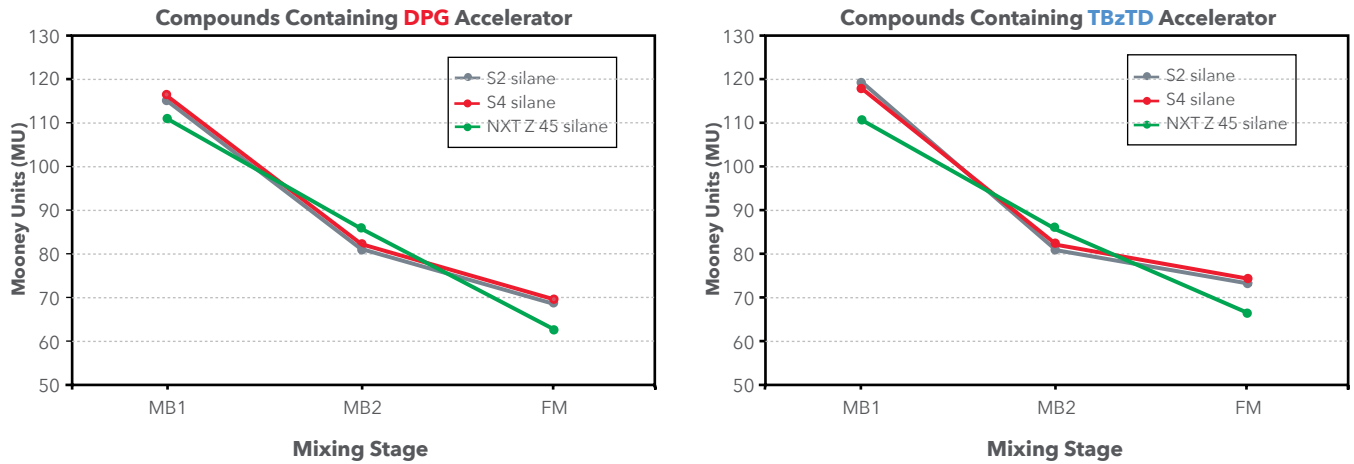

Note: Test results. Actual results may vary.

Table 3: NXT Z 45 Silane Typical Physical Properties Increase When TBzTD is Substituted for DPG


Ingredients	Units	Compounds with DPG (2.0 phr)			Compounds with TBzTD (0.3 phr)		
		S2	S4	NXT Z 45 Silane	S2	S4	NXT Z 45 Silane
<b>Cure Package</b>							
Sulfur		1.865	1.100	1.675	1.830	1.065	1.640
CBS	phr	2.0	2.0	2.0	2.0	2.0	2.0
DPG		2.0	2.0	2.0			
Total Sulfur Atoms (x 10 <sup>22</sup> )		4.93	4.93	3.82	4.93	4.93	3.82
Scorch at 135 °C, t3	min	15	12	6	25	14	21
Scorch at 135 °C, t10	min	18	16	7	27	17	24
100% Modulus	MPa	2.8	2.7	2.7	2.7	2.6	2.9
300% Modulus	MPa	13.0	12.2	14.0	12.8	12.0	14.2
RI (M300/M100)		4.6	4.5	5.2	4.7	4.6	4.9
Elongation	%	332	364	322	325	403	404
Shore A at RT	shore A	70	70	65	70	71	68
Graves Tear at 100 °C		35	37	32	31	37	33
DIN Abrasion (normalized)	%	94	100	123	101	98	122
Heat Build Up, Delta Temp.	°C	17	18	13	17	18	13
Percent Set	%	14	15	9	12	13	8

Typical physical properties are average data and are not to be used as or to develop specifications.

Table 4: Comparison of Rebound Values for Rubber Compounds Containing S2 (TESPD) Silane, S4 (TESPT) Silane or NXT Z 45 Silane Having a Cure Package of CBS and DPG Versus CBS and TBzTD

Rebound	Units	Compounds with <b>DPG</b> (2.0 phr)			Compounds with <b>TBzTD</b> (0.3 phr)		
		S2	S4	NXT Z 45 Silane	S2	S4	NXT Z 45 Silane
0 °C	%	8	9	6	8	8	7
RT	%	20	21	23	20	21	23
70 °C	%	40	40	45	41	41	47
100 °C	%	49	49	54	50	50	52
100 °C - RT	%	29	28	31	30	29	29

Figure 3: E' Strain Sweep of Rubber Compounds Containing S2 (TESPD) Silane, S4 (TESPT) Silane or NXT Z 45 Silane Having a Cure Package of CBS and DPG Versus CBS and TBzTD

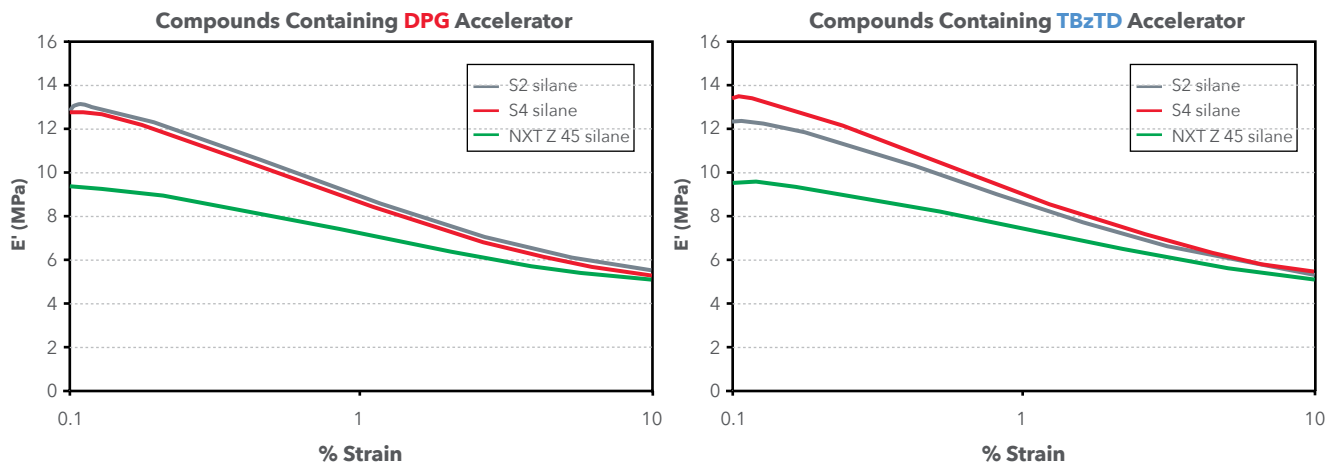

Note: Test results. Actual results may vary.

Figure 4: E'' Strain Sweep of Rubber Compounds Containing S2 (TESPD) Silane, S4 (TESPT) Silane or NXT Z 45 Silane Having a Cure Package of CBS and DPG Versus CBS and TBzTD



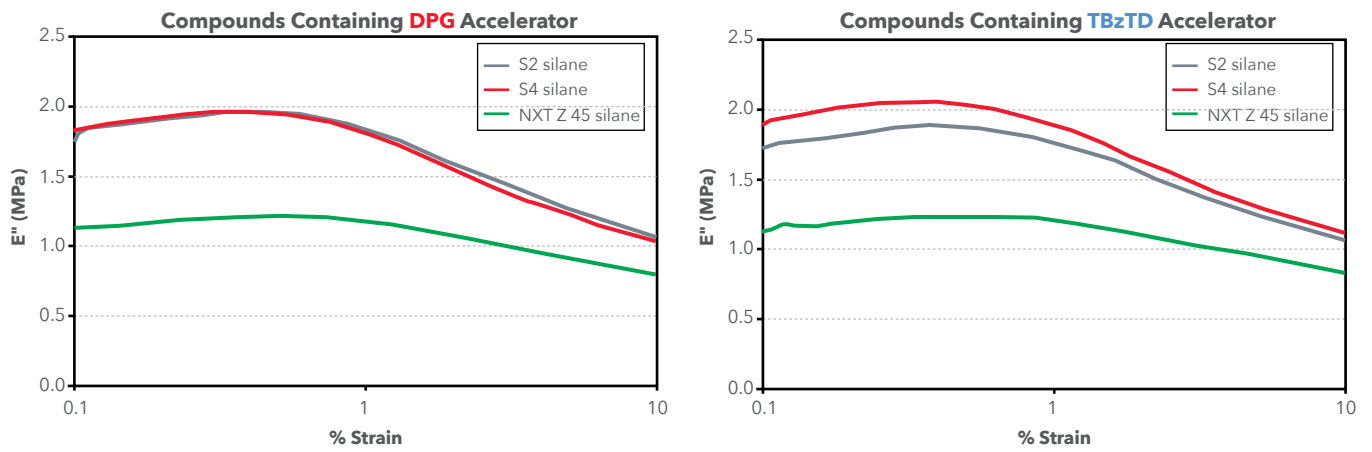


Figure 5: Tan δ Max Values for Rubber Compounds Containing S2 (TESPD) Silane, S4 (TESPT) Silane or NXT Z 45 Silane Having a Cure Package of CBS and DPG Versus CBS and TBzTD

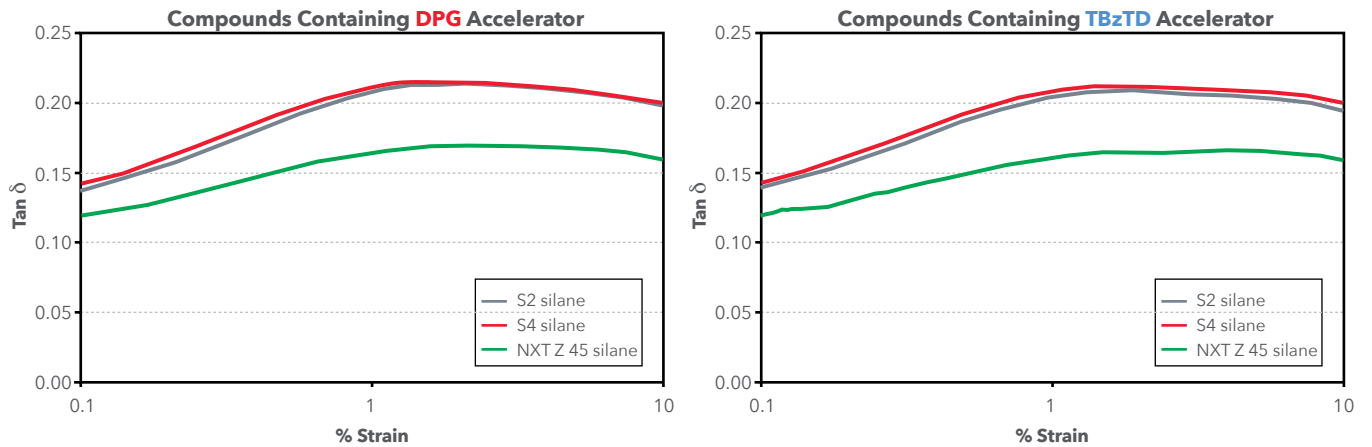

Note: Test results. Actual results may vary.

Figure 6: Temperature Sweep of S2 (TESPD) Silane, S4 (TESPT) Silane or NXT Z 45 Silane Rubber Compounds Having a Cure Package of CBS and DPG Versus CBS and TBzTD

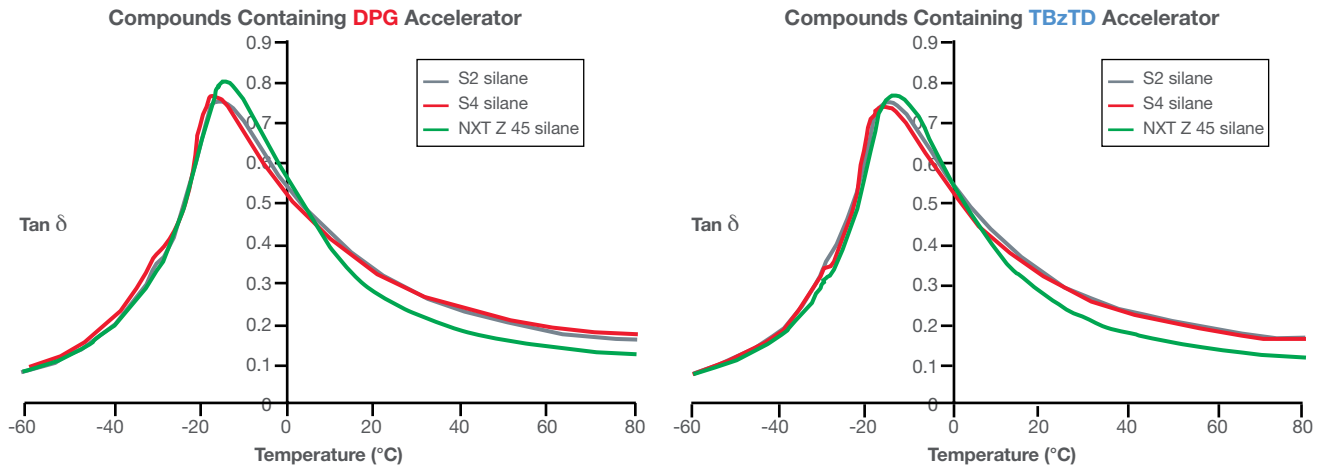

Note: Test results. Actual results may vary.

Table 5: Mix Procedure for NXT Z 45 Silane

1.6L Banbury Mixer, 80 rpm, 70% FF		
Time	T (°C)	Ingredients
<b>Masterbatch (MB1)</b>		
0:00	70	Polymers
0:40		1/2 silica, silane
1:30		1/2 silica, chemicals
2:30	125	Carbon black, Oil
4:00	135	Sweep
6:00	155	Discharge
		<i>Mill Blend</i>
<b>Masterbatch (MB2)</b>		
0:00	70	Add MB1
1:00		Add any chemicals
2:00	135	Sweep
4:00	155	Discharge
		<i>Mill Blend</i>
<b>Final Mix (Productive Mix)</b>		
0:00	50	Add MB2, Cure Package at 50 rpm
3:10	105	Discharge
		<i>Mil Blend</i>

**Patent Status**

Nothing contained herein shall be construed to imply the nonexistence of any relevant patents or to constitute the permission, inducement or recommendation to practice any invention covered by any patent, without authority from the owner of the patent.

**Limitations**

Customers must evaluate Momentive Performance Materials products and make their own determination as to fitness of use in their particular applications.

**Product Safety, Handling and Storage**

Customers should review the latest Safety Data Sheet (SDS) and label for product safety information, safe handling instructions, personal protective equipment if necessary, emergency service contact information, and any special storage conditions required for safety. Momentive Performance Materials (MPM) maintains an around-the-clock emergency service for its products. SDS are available at [www.momentive.com](http://www.momentive.com) or, upon request, from any MPM representative.

For product storage and handling procedures to maintain the product quality within our stated specifications, please review Certificates of Analysis, which are available in the Order Center. Use of other materials in conjunction with MPM products (for example, primers) may require additional precautions. Please review and follow the safety information provided by the manufacturer of such other materials.

**Customer Service Centers**

**Worldwide**

Email: [commercial.services@momentive.com](mailto:commercial.services@momentive.com)

**Americas**

+1 800 295 2392  
+1 614 986 2495

**Europe, Middle East,  
Africa and India**

00800 4321 1000  
+40 213 044229

**Asia Pacific**

**China**  
800 820 0202  
+86 21 3860 4892

**Japan**  
0120 975 400  
+81 276 20 6182

**All Other Countries**  
+60 3 9206 1543

**Disclaimer**

THE MATERIALS, PRODUCTS AND SERVICES OF MOMENTIVE PERFORMANCE MATERIALS INC. AND ITS SUBSIDIARIES AND AFFILIATES (COLLECTIVELY "SUPPLIER"), ARE SOLD SUBJECT TO SUPPLIER'S STANDARD CONDITIONS OF SALE, WHICH ARE INCLUDED IN THE APPLICABLE DISTRIBUTOR OR OTHER SALES AGREEMENT, PRINTED ON THE BACK OF ORDER ACKNOWLEDGMENTS AND INVOICES, AND AVAILABLE UPON REQUEST. ALTHOUGH ANY INFORMATION, RECOMMENDATIONS, OR ADVICE CONTAINED HEREIN IS GIVEN IN GOOD FAITH, SUPPLIER MAKES NO WARRANTY OR GUARANTEE, EXPRESS OR IMPLIED, (i) THAT THE RESULTS DESCRIBED HEREIN WILL BE OBTAINED UNDER END-USE CONDITIONS, OR (ii) AS TO THE EFFECTIVENESS OR SAFETY OF ANY DESIGN INCORPORATING ITS PRODUCTS, MATERIALS, SERVICES, RECOMMENDATIONS OR ADVICE. EXCEPT AS PROVIDED IN SUPPLIER'S STANDARD CONDITIONS OF SALE, SUPPLIER AND ITS REPRESENTATIVES SHALL IN NO EVENT BE RESPONSIBLE FOR ANY LOSS RESULTING FROM ANY USE OF ITS MATERIALS, PRODUCTS OR SERVICES DESCRIBED HEREIN. Each user bears full responsibility for making its own determination as to the suitability of Supplier's materials, services, recommendations, or advice for its own particular use. Each user must identify and perform all tests and analyses necessary to assure that its finished parts incorporating Supplier's products, materials, or services will be safe and suitable for use under end-use conditions. Nothing in this or any other document, nor any oral recommendation or advice, shall be deemed to alter, vary, supersede, or waive any provision of Supplier's standard Conditions of Sale or this Disclaimer, unless any such modification is specifically agreed to in a writing signed by Supplier. No statement contained herein concerning a possible or suggested use of any material, product, service or design is intended, or should be construed, to grant any license under any patent or other intellectual property right of Supplier covering such use or design, or as a recommendation for the use of such material, product, service or design in the infringement of any patent or other intellectual property right.